

Direct observation of interacting Kondo screened $4f$ moments in CePt_5 with XMCD

C. Praetorius, A. Koehl,^{*} B. Muenzing, H. Bardenhagen, and K. Fauth[†]

Physikalisches Institut, Universität Würzburg, Am Hubland, D-97074 Würzburg

(Dated: March 1, 2013)

Abstract

We use x-ray absorption and magnetic circular dichroism to study electronic configuration and local susceptibility of $\text{CePt}_5/\text{Pt}(111)$ surface alloys from well above to well below the impurity Kondo temperature. The anisotropic paramagnetic response is governed by the hexagonal crystal field and ferromagnetic correlations with modified parameters for Ce moments residing next to the alloy surface. Quantitative XMCD evaluations provide direct evidence of Kondo screening of both spin and orbital $4f$ moments. Magnetic signatures of coherence are not apparent for $T \geq 13$ K.

PACS numbers: 71.27.+a, 75.30.Mb, 75.70.-i, 78.70.Dm

Kondo and heavy fermion systems display fascinating many body phenomena caused by the interplay of localized and itinerant electronic degrees of freedom. Despite their local character, hybridization and on site Coulomb repulsion give rise to unconventional macroscopic behavior and complex phase diagrams [1, 2]. Dilute magnetic impurities induce a many body singlet ground state, resulting from effective antiferromagnetic interaction between localized and delocalized base states [1, 3–5]. Accordingly, a considerable density of excitations develops on the scale of the singlet formation energy gain, frequently referred to as the Kondo scale $k_B T_K$. While the phenomenology of Kondo physics is often explored with macroscopic probes of the low temperature quasiparticle excitations, electron spectroscopies detect them as the Kondo resonance near the Fermi energy [6–8]. Involving core levels adds element and orbital specificity and may allow observing the effective impurity valence [9–11].

Hybridization and singlet formation being intertwined, T_K sets the scales of both the change of average impurity orbital occupation and the screening of its effective paramagnetic moment. As a result, the magnetic response gradually changes from being Curie-Weiss like at $T \gg T_K$ towards a finite, Pauli-like susceptibility as $T \rightarrow 0$. This generic behavior is well accounted for by the single impurity Anderson and Kondo models and remains essentially valid at elevated impurity density as long as $T \gtrsim T_K$. In Kondo lattices the coherence temperature T^* emerges as a yet lower energy scale. It characterizes the onset of interactions between impurities, which ultimately lead to the formation of coherent heavy-fermion bands at $T \ll T^*$ [1].

Hybridization concurrently induces indirect magnetic coupling between the localized moments, leading to a competition between the tendencies to screen the local moments on one hand and to order finite moments on the other [1, 12, 13]. It is therefore interesting to specifically observe the local magnetic moments in dense Kondo systems across a temperature window ranging from well above to well below the Kondo temperature. Element and orbital specificity in probing magnetic response can be provided by means of spectroscopy, i. e. x-ray absorption (XA) and magnetic circular dichroism (XMCD) [14]. XMCD determines the magnetic polarization of the impurity orbitals and hence provides an adequate measure of local susceptibility. We demonstrate below that XMCD measurements on a sufficiently well defined Kondo lattice system allows addressing all essential ingredients governing magnetic behavior, i. e. crystal field (CF) splitting, Kondo screening and magnetic coupling.

Previous attempts at observing the magnetic response of Ce based Kondo or heavy fermion materials by XMCD appear to have been of limited success. In all instances the Ce moments indicated Curie-Weiss like $4f$ behavior, even where bulk magnetization clearly showed a transition to a Pauli type paramagnetism [15–20]. Various mechanisms have been proposed to account for the apparent failure of XMCD to reproduce the macroscopic magnetic characteristics. Our results below indicate that the surface sensitivity of electron yield measurements is a likely cause of the observed discrepancies.

For the present work we have chosen an approach where the relevant physics is confined to a thin layer at specimen surfaces, ideally matching the probing depth of XMCD. For the specific system in question, ordered CePt₅ surface alloys prepared on Pt(111) substrates, the Kondo resonance [21–23] and even signatures of incipient coherence [24] have been observed previously.

As established in previous work [25–27] thin Ce-Pt surface alloy films were prepared in situ by evaporation of Ce onto clean Pt(111) and subsequent annealing to ≈ 900 K. The alloy film thickness was controlled by the amount of deposited Ce. Hexagonal LEED patterns indicated 2×2 superstructures with thickness dependent orientation and partial relaxation of the lateral tensile strain exerted by the substrate, qualitatively well in accordance with the literature. Here we primarily present and discuss results obtained for an alloy layer containing ≈ 4 hexagonal atomic CePt₂ planes (equiv. to Ref. 24). For comparison, we also use data collected at 30% of this initial Ce coverage, a non-rotated hexagonal 2×2 alloy with reduced sharpness of the electron diffraction spots.

Ce M_{4,5} XA and XMCD spectra were acquired in the total electron yield mode (TEY) with a custom ultrahigh vacuum superconducting magnet apparatus, attached to the PM3 bending magnet beamline at the BESSY II synchrotron radiation facility in Berlin, Germany. XMCD was measured at constant helicity ($p \approx 0.93$) and by alternating the applied field ($\mu_0 H = \pm 1.5$ T) at every photon energy setting. Magnetic anisotropy was probed by taking normal ($\theta = 0^\circ$) and off normal incidence ($\theta = 60^\circ$) spectra in the temperature range $13 \text{ K} < T < 270 \text{ K}$. The XMCD response consistently proved linear in the applied field. We hence take the Ce polarization at finite field as a measure of the local paramagnetic $4f$ susceptibility. Total Ce $4f$ moments μ_{Ce} are derived from the orbital moment sum rule [28] assuming the atomic value $g = 6/7$ for the Landé factor and hence $\mu_{Ce} = 0.75\mu_L$. This procedure is most appropriate since the μ_L sum rule is robust in the light rare earth metals

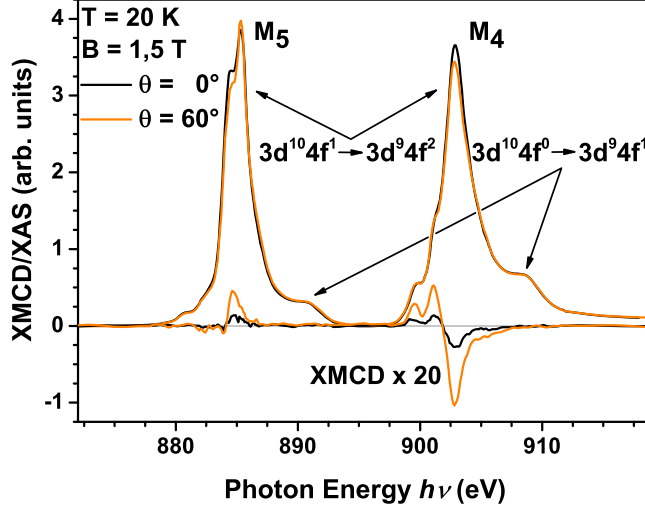


FIG. 1: Normal and oblique incidence Ce $M_{4,5}$ XA and XMCD spectra (average and difference, respectively, of data taken at $\mu_0 H = \pm 1.5$ T) of 4 u. c. CePt₅/Pt(111).

[29, 30], whereas proper evaluation of the spin sum rule is impeded by strong configuration interaction between M_5 and M_4 excitations [30–32]. Still, XMCD sum rule evaluations require the TEY to be linear in the XA cross section, which critically depends on the ratio of absorption length and electron escape depth λ_e [33, 34]. Beyond the material presented below, we have therefore collected auxiliary angle and alloy thickness dependent datasets from which we determine $\lambda_e \approx 1.5 \dots 2$ nm and conclude that TEY saturation induced relative errors in the magnetic moment evaluations amount to less than 5%. The experimental λ_e , while comparable to the late $3d$ metals [33], is considerably smaller than frequently assumed for rare earth materials [15, 34]. XMCD experiments with TEY detection thus require particular caution, especially when a comparison to bulk properties is aimed at [35]. A more detailed account of thickness dependent XA and XMCD results shall be given elsewhere [36].

Fig. 1 shows normal and grazing incidence Ce $M_{4,5}$ XA and XMCD spectra of the CePt₅ film at $T = 20$ K. The XA spectra are composed of a multiplet and a high energy shoulder corresponding to core excited states of f^2 and f^1 character, respectively [9, 31, 35, 37]. The appearance of the latter in the XA spectra reflect an f^0 admixture in the initial state valence configuration. The Kondo interaction entails a temperature dependent $4f$ occupation $n_{4f}(T/T_K)$ [1, 38] and relative $f^0 \rightarrow f^1$ spectral weights can be used to estimate T_K [37, 39].

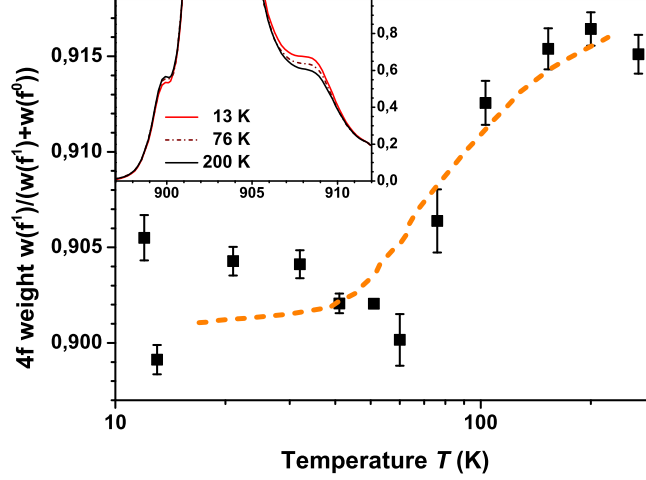


FIG. 2: Evolution of n_{4f} with temperature, evaluated from f^1 and f^0 initial state spectral weights (symbols). Single impurity n_{4f} in non-crossing approx., extracted from Ref. 38 (rescaled, dashed line). Inset: detail of Ce M_4 XA spectra, highlighting the temperature dependent f^0 spectral weight.

Due to incomplete knowledge about, e. g., initial and excited state hybridization, the determination of n_{4f} from XA experiments is not fully quantitative. Comparing the maximum relative changes of the f^1 and f^0 initial state spectral weights we estimate that $n_{4f} \approx 0.9$ in the low temperature limit. On this basis we plot n_{4f} vs. specimen temperature in Fig. 2. Along with the experimental data, we show rescaled calculated results for the single impurity Kondo problem from Ref. 38. The good agreement reflects the well-known observation that the high temperature ($T \gtrsim T_K$) behaviour of heavy fermion systems resembles the one of single impurities [1]. Based on this comparison, we estimate $T_K \approx 85$ K, fully in line with the observation of the Kondo resonance at $T = 66$ K in photoemission. [24].

Returning to the XA and XMCD data in Fig. 1, we observe minor spectral differences between normal and off normal incidence spectra, i. e. small linear dichroism owing to the hexagonal symmetry. By contrast, the magnetic anisotropy derived from the XMCD magnitude is much stronger and amounts to about $\chi_{60^\circ}/\chi_{0^\circ} = 4$ at $T = 20$ K, which translates to an anisotropy $\chi_{\parallel}/\chi_{\perp} = 5$ between the susceptibilities along and perpendicular to the hexagonal axis, respectively. The m_J levels of the $4f^1$ configuration not being mixed by a hexagonal CF, we can unanimously determine the ground level from the single ion anisotropy. Based

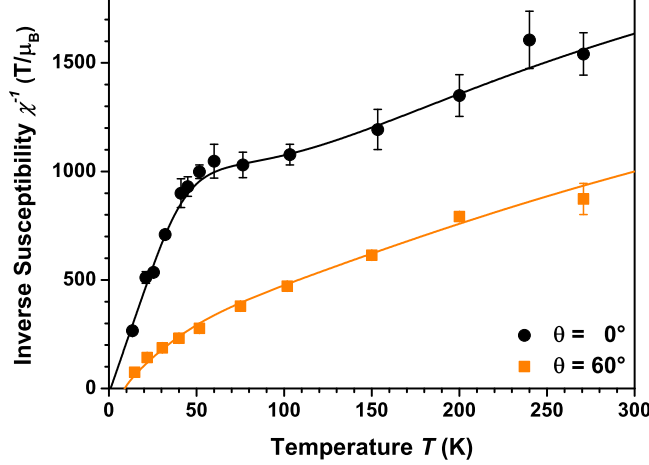


FIG. 3: Symbols: normal and off-normal incidence inverse local Ce 4*f* susceptibility, derived from XMCD. Lines: Curie-Weiss fits to $\chi_{0^\circ, 60^\circ}^{-1}$ with $\Delta_{1,2}$ as given in the text.

on second order expressions for the susceptibility [40] we write the anisotropy as

$$\frac{\chi_{\parallel}}{\chi_{\perp}} = \frac{9 + \frac{16k_B T}{\Delta_1} - \left(\frac{16k_B T}{\Delta_1} - \frac{10k_B T}{\Delta_2 - \Delta_1} \right) e^{\frac{-\Delta_1}{k_B T}} - \frac{10k_B T}{\Delta_2 - \Delta_1} e^{\frac{-\Delta_2}{k_B T}}}{1 + 9e^{\frac{-\Delta_1}{k_B T}} + 25e^{\frac{-\Delta_2}{k_B T}}}$$

which only depends on temperature and the CF splitting, given by $\Delta_1 = E_{3/2} - E_{1/2}$ and $\Delta_2 = E_{5/2} - E_{1/2}$. It follows that the observed magnetic anisotropy cannot be obtained unless $m_J = 1/2$ is the ground level, in line with the analysis of polycrystalline CePt₅ in Ref. 40.

In the limit of $k_B T \ll \Delta_1, \Delta_2$ and in absence of magnetic coupling between Ce sites, the paramagnetic response is expected to follow a Curie law with a reduced 4*f* moment compared to the free ion value ($2.54\mu_B$). For the $m_J = 1/2$ ground level one obtains $\mu_{1/2} = g\sqrt{3/4}\mu_B$ along the hexagonal axis. To additionally allow for Kondo screening we introduce an effective moment, related to the local susceptibility via $\chi_{loc} = \mu_{eff}^2/3k_B T$.

Figure 3 plots the inverse local Ce 4*f* susceptibility vs. temperature in the range of 13 K $\leq T \leq 270$ K. The pronounced slope changes in the normal incidence $\chi_{\parallel}^{-1}(T)$ are due to the CF level structure and are adequately accounted for with $\Delta_1 = 16 \pm 1$ meV and $\Delta_2 = 91 \pm 15$ meV. We note that Δ_1 is significantly smaller than the corresponding value (28 meV) in bulk CePt₅ [40] as a consequence of the dilated CePt₅ lattice when grown on Pt(111). Thickness dependent measurements at different levels of strain relaxation confirm this assignment [36]. The low temperature magnetic response obviously follows a Curie-Weiss law with positive paramagnetic Curie-Weiss temperature Θ_p , indicative of ferromagnetic correlations

in the alloy film. The angle dependence of Θ_p derives from the anisotropic effective moment. Allowing a Weiss mean field we write the inverse local susceptibility as $\chi_{loc}^{-1} = 3k_B T / \mu_{eff}^2 + \lambda$ and see that μ_{eff} can be evaluated at low temperature from the slope of χ_{loc}^{-1} , irrespective of the coupling strength λ .

The low temperature $4f$ moment resulting from the $\chi_{\parallel}^{-1}$ data of Fig. 3 amounts to $\mu_{eff} = 0.43(2)\mu_B$, and is thus reduced to below 60% of the expected value. We take this as immediate evidence of Kondo screening of the local Ce moment. The essentially temperature independent XMCD spectral shape clearly indicates that spin and orbital parts of the Ce $4f$ moment are screened alike, as expected from the Coqblin-Schrieffer model [41]. Calculated scenarios do report on relative moment reductions of the same order upon cooling through the Kondo temperature [42, 43]. In our experiments we thus directly observe partially screened Ce $4f$ moments with mutual interactions of predominantly ferromagnetic character.

These findings appear to contrast the observation of antiferromagnetism in bulk CePt₅ at very low temperature ($T_N = 1$ K) [44]. We suggest that our observations result from the specimen geometry: in the ultrathin surface alloys, the magnetic fluctuations may be dominated by interactions within the atomic layers hosting the Ce atoms, while interlayer interactions might become important at lower temperatures and with a larger number of layers, only. Concerning ordering within the hexagonal CePt₂ planes, our data suggest a possible ferromagnetic instability at $T \lesssim 10$ K. Accordingly, we conjecture that the volume phase of CePt₅ probably is a layer wise (type II) antiferromagnet.

The numerical results for the CF energies Δ_1, Δ_2 call for a cross check of the magnitude of the magnetic anisotropy on the basis of the formula given above. Indeed, a larger anisotropy is expected with these CF level splittings, further enhanced by the magnetic coupling ($\Theta_p > 0$). Given the surface sensitivity of XMCD one might suspect the occurrence of a modified magnetic anisotropy at the surface. We have therefore investigated an alloy film of reduced thickness for comparison, as outlined above. XA spectra at high and low temperature, respectively, show magnitudes of f^0 initial state character and valence change upon cooling which are comparable to the data presented in Figs. 1 and 2, suggesting a similar Kondo screening to occur. The XMCD response, however, is significantly altered (Fig. 4), simultaneously being enhanced at normal incidence and reduced in off-normal geometry. The resulting magnetic anisotropy is considerably reduced ($\chi_{60^\circ}/\chi_{0^\circ} = 1.6$ at 20

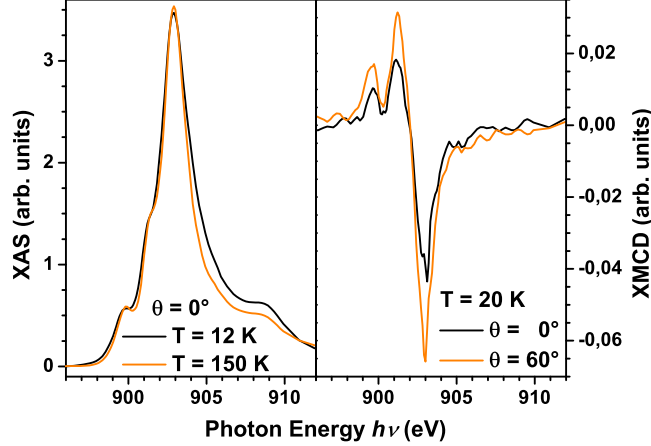


FIG. 4: a) Ce M_4 XA at low thickness with increased f^0 weight at low temperature. b) Normal and off-normal Ce M_4 XMCD at 20 K with reduced anisotropy compared to Fig. 1.

K) compared to the thicker alloy film. The assumption of the subsurface CePt_2 layer possessing a strongly reduced anisotropy and a homogeneous CePt_5 film underneath provides a consistent scenario for our observation and proves to be in accordance with results on a wider range of surface alloy thickness [36]. Such a modification can readily be rationalized as to arise from the different coordination of the Ce atoms in the topmost Ce-containing layer. In particular, a strong reduction of Δ_1 would provide a rational basis for reduced magnetic anisotropy of the surface-near Ce ions. These considerations strongly underline that great caution is required when applying surface sensitive methods to rare earth alloys. In the present case, the discrimination of surface vs. “bulk” properties is facilitated by the fact that reasonably well ordered alloy films can be prepared over an extended range of alloy thickness.

We finally note that the Ce $4f$ susceptibility does not bend off to a finite, temperature independent value. Thus, while impurity Kondo screening is evident in our experimental data, there is no obvious signature of coherence for $T \geq 13$ K, suggesting a lower scale for the full development of the heavy fermion state. In addition, the proximity to a ferromagnetic instability may stabilize the Curie-Weiss behavior in the CePt_5 surface alloys.

In conclusion, we have presented an experimental investigation of the magnetic response of a Kondo lattice by examining the local Ce $4f$ susceptibility in ordered CePt_5 surface alloys with XMCD. Thin film Kondo lattices prove an ideal match to the surface sensitivity of XMCD in the TEY mode. Varying the alloy thickness allows assessing the importance

of surface induced modifications to the magnetic properties. While the anisotropic paramagnetic response allows characterizing the hexagonal CF, the quantitative XMCD sum rule evaluation reveals the Kondo-screened nature of the Ce moments. Our finding of a positive Curie Weiss temperature suggests a ferromagnetic instability to occur around $T \lesssim 10$ K, presumably due to RKKY coupling within the hexagonal CePt₂ planes. It will be most interesting to carry through these investigations to lower temperatures in order to follow the evolution to a potentially magnetically ordered coherent heavy fermion state. Due to its inherent element and orbital specificity, direct evidence of both ordered and screened local moments would be provided by XMCD. Work along these lines is currently in progress.

We gratefully acknowledge the support by the BESSY staff, R. Follath, T. Kachel and H. Pfau in particular. This work was financially supported by the Deutsche Forschungsgemeinschaft within research unit FOR1162. Additional partial funding through BMBF under contract no. 05ES3XBA/5 is gratefully acknowledged.

* present address: Peter Grünberg Institut, Forschungszentrum Jülich, 52425 Jülich, Germany

† fauth@physik.uni-wuerzburg.de

- [1] A. C. Hewson, *The Kondo Problem to Heavy Fermions* (Cambridge University Press, 1993).
- [2] H. von Löhneysen, A. Rosch, M. Vojta, and P. Wölfle, Rev. Mod. Phys. **79**, 1015 (2007).
- [3] J. Kondo, Prog. Theor. Phys. **32**, 37 (1964).
- [4] N. Andrei, K. Furuya, and J. H. Lowenstein, Rev. Mod. Phys. **55**, 331 (1983).
- [5] N. E. Bickers, Rev. Mod. Phys. **59**, 845 (1987).
- [6] D. Ehm, S. Hüfner, F. Reinert, J. Kroha, P. Wölfle, O. Stockert, C. Geibel, and H. von Löhneysen, Phys. Rev. B **76**, 045117 (2007).
- [7] M. Grioni, P. Weibel, D. Malterre, Y. Baer, and L. Duo, Phys. Rev. B **55**, 2056 (1997).
- [8] Ternes, A. J. Heinrich, and W. Schneider, J. Phys. Cond. Matter **21**, 053001 (2009).
- [9] J. C. Fuggle, F. U. Hillebrecht, J. M. Esteva, R. C. Karnatak, O. Gunnarsson, and K. Schönhammer, Phys. Rev. B **27**, 4637 (1983).
- [10] D. Malterre, M. Grioni, and Y. Baer, Adv. Phys. **45**, 299 (1996).
- [11] C. Laubschat, Appl. Phys. A **65**, 573 (1997).
- [12] S. Doniach, Physica B **91**, 231 (1977).

- [13] B. Coqblin, *Acta Phys. Pol. A* **118**, 913 (2005).
- [14] G. Schütz, E. Goering, and H. H. Stoll, in *Handbook of Magnetism and Advanced Magnetic Materials*, edited by H. Kronmüller and S. Parkin (Wiley, 2007), vol. 3, p. 1311.
- [15] S. Nakamura, T. Yoshida, Y. Takayama, T. Miyahara, H. Ishii, H. Sugawara, H. Sato, and T. Nakamura, *J. Phys. Soc. Jpn.* **75**, 044707 (2006).
- [16] T. Miyahara, H. Ishii, Y. Takayama, M. Hirose, K. Maruyama, K. Obu, M. Shinoda, T. Muro, Y. Saitoh, T. D. Matsuda, et al., *J. Phys. Soc. Jpn.* **70**, 2977 (2001).
- [17] T. Miyahara, H. Ishii, K. Obu, M. Shinoda, Y. Takayama, T. Muro, T. D. Matsuda, H. Sugawara, and H. Sato, *Surf. Rev. Lett.* **9**, 831 (2002).
- [18] T. Miyahara and H. Shiozawa, *J. Electron Spectrosc. Relat. Phenom.* **136**, 117 (2004).
- [19] H. Shiozawa, T. Miyahara, H. Ishii, Y. Takayama, K. Obu, T. Muro, Y. Saitoh, T. D. Matsuda, H. Sugawara, and H. Sato, *Nucl Instrum. Meth. B* **199**, 318 (2003).
- [20] H. Shiozawa, T. Miyahara, K. Obu, Y. Takayama, H. Ishii, T. D. Matsuda, H. Sugawara, H. Sato, T. Muro, and Y. Saitoh, *J. Phys. Soc. Jpn.* **72**, 2079 (2003).
- [21] A. B. Andrews, J. J. Joyce, A. J. Arko, J. D. Thompson, J. Tang, J. M. Lawrence, and J. C. Hemminger, *Phys. Rev. B* **51**, 3277 (1995).
- [22] M. Garnier, D. Purdie, K. Breuer, M. Hengsberger, and Y. Baer, *Phys. Rev. B* **56**, 11399 (1997).
- [23] M. Garnier, D. Purdie, K. Breuer, M. Hengsberger, and Y. Baer, *Phys. Rev. B* **58**, 9697 (1998).
- [24] M. Klein, A. Nuber, H. Schwab, C. Albers, N. Tobita, M. Higashiguchi, J. Jiang, S. Fukuda, K. Tanaka, K. Shimada, et al., *Phys. Rev. Lett.* **106**, 186407 (2011).
- [25] J. Tang, J. M. Lawrence, and J. C. Hemminger, *Phys. Rev. B* **48**, 15342 (1993).
- [26] C. J. Baddeley, A. W. Stephenson, C. Hardacre, M. Tikhov, and R. M. Lambert, *Phys. Rev. B* **56**, 12589 (1997).
- [27] J. M. Essen, C. Becker, and K. Wandelt, *e-J. Surf. Sci. Nanotech.* **7**, 421 (2009).
- [28] B. T. Thole, P. Carra, F. Sette, and G. van der Laan, *Phys. Rev. Lett.* **68**, 1943 (1992).
- [29] G. van der Laan, *Phys. Rev. B* **57**, 112 (1998).
- [30] J. P. Schillé, F. Bertran, M. Finazzi, C. Brouder, J. P. Kappler, and G. Krill, *Phys. Rev. B* **50**, 2985 (1994).
- [31] B. T. Thole, G. van der Laan, J. C. Fuggle, G. A. Sawatzky, R. C. Karnatak, and J. M.

- Esteva, Phys. Rev. B **32**, 5107 (1985).
- [32] Y. Teramura, A. Tanaka, B. T. Thole, and T. Jo, J. Phys. Soc. Jpn. **65**, 3056 (1996).
 - [33] R. Nakajima, J. Stöhr, and Y. U. Idzerda, Phys. Rev. B **59**, 6421 (1999).
 - [34] M. Abbate, J. B. Goedkoop, F. M. F. Degroot, M. Grioni, J. C. Fuggle, S. Hofmann, H. Petersen, and M. Sacchi, Surf. Interface Anal. **18**, 65 (1992).
 - [35] C. Dallera, M. Grioni, A. Palenzona, M. Taguchi, E. Annese, G. Ghiringhelli, A. Tagliaferri, N. B. Brookes, T. Neisius, and L. Braicovich, Phys. Rev. B **70**, 085112 (2004).
 - [36] C. Praetorius and K. Fauth, to be published.
 - [37] A. Delobbe, M. Finazzi, B. Buschinger, O. Trovarelli, C. Geibel, J. P. Kappler, and G. Krill, Physica B **259-61**, 1144 (1999).
 - [38] N. E. Bickers, D. L. Cox, and J. W. Wilkins, Phys. Rev. B **36**, 2036 (1987).
 - [39] J. Rothman, C. Meyer, D. Givord, J. Vogel, M. Finazzi, A. Fontaine, J. P. Kappler, and N. B. Brookes, J. Magn. Magn. Mater. **198-99**, 276 (1999).
 - [40] H. Lueken, M. Meier, G. Klessen, W. Bronger, and J. Fleischhauer, J. Less-Comm. Met. **63**, P35 (1979).
 - [41] B. Coqblin and Schrieffer, Phys. Rev. **185**, 847 (1969).
 - [42] K. S. D. Beach and F. F. Assaad, Phys. Rev. B **77**, 205123 (2008).
 - [43] G.-B. Li, G.-M. Zhang, and L. Yu, Phys. Rev. B **81**, 094420 (2010).
 - [44] A. Schröder, R. Vandenberg, H. von Löhneysen, W. Paul, and H. Lueken, Solid State Commun. **65**, 99 (1988).